

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE August 16, 1999		3. REPORT TYPE AND DATES COVERED Technical Report # 47	
4. TITLE AND SUBTITLE Thiophene-Linked Polyphenylquinoxaline: A New Electron Transport Conjugated Polymer for Electroluminescent Devices.				5. FUNDING NUMBERS N00014-94-1-0540 Kenneth J. Wynne R & T Code 3132111	
6. AUTHOR(S) Y. Cui, X. Zhang and S. A. Jenekhe					
7. PERFORMING ORGANIZATION NAMES(S) AND ADDRESS(ES) University of Rochester Department of Chemical Engineering 206 Gavett hall, Box 270166 Rochester, NY 14627-0166				8. PERFORMING ORGANIZATION REPORT NUMBER # 47	
9. SPONSORING / MONITORING AGENCY NAMES(S) AND ADDRESS(ES) Office of Naval Research 800 North Quincy Street Arlington, VA 22217-5000				10. SPONSORING / MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES Published in MACROMOLECULES, 1999, 32, 3824-3826.					
a. DISTRIBUTION / AVAILABILITY STATEMENT Reproduction in whole or in part is permitted for any purpose of the United States Government. This document has been approved for public release and sale; its distribution is unlimited.				12. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words)  A new n-type conjugated polymer, poly[2,2'-(thiophene-2,5-diyl)-6,6'-bis(3-phenylquinoxaline)] (PTQx), was synthesized, characterized, and shown to be an excellent electron transport polymer for electroluminescent devices. PTQx thin films had a reversible electrochemical reduction but an irreversible oxidation, confirming its n-type nature. Electron affinity and ionization potential of PTQx thin films were estimated from cyclic voltammetry to be 3.0 and 5.54 eV, respectively. Poly(phenylene vinylene) (PPV) based light emitting diodes using PTQx as an electron transport layer, ITO/PPV/PTQx/Al, combined low turn-on voltage (3.6 eV) and high brightness (710 cd/m <sup>2</sup> ) with good efficiency (0.4%). The performance of PTQx as an electron transport material in electroluminescent devices was found to be far superior compared to all previously reported n-type polymers.					
14. SUBJECT TERMS Polyquinoxaline; electron transport polymer; electroluminescence; n-type polymer; poly(phenylene vinylene); oligoquinoxaline.				15. NUMBER OF PAGES 23	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT Unlimited		

19990823 067

Standard Form 298 (Rev. 2-89)  
Prescribed by ANSI Std Z39-18  
298-102

DTIC QUALITY INSPECTED 4

OFFICE OF NAVAL RESEARCH

GRANT NO: N00014-94-1-0540

R&T Code 3132111

Kenneth J. Wynne

Technical Report NO. 47

Thiophene-Linked Polyphenylquinoxaline: A New Electron  
Transport Conjugated Polymer for Electroluminescent Devices

By

Y. Cui, X. Zhang and S. A. Jenekhe  
Published

In

MACROMOLECULES

Departments of Chemical Engineering  
and Chemistry  
University of Rochester, New York 14627

August 16, 1999

Reproduction in whole or in part is permitted for any purpose  
of the United States Government

This document has been approved for public release and sale;  
its distribution is unlimited.

**Thiophene-Linked Polyphenylquinoxaline: A New Electron Transport Conjugated Polymer for Electroluminescent Devices**

Yuanting Cui, Xuejun Zhang, and Samson A. Jenekhe\*  
Departments of Chemical Engineering and Chemistry  
University of Rochester, Rochester, New York 14627-0166

**Abstract**

A new n-type conjugated polymer, poly[2,2'-(thiophene-2,5-diyl)-6,6'-bis(3-phenylquinoxaline)] (PTQx), was synthesized, characterized, and shown to be an excellent electron transport polymer for electroluminescent devices. PTQx thin films had a reversible electrochemical reduction but an irreversible oxidation, confirming its n-type nature. Electron affinity and ionization potential of PTQx thin films were estimated from cyclic voltammetry to be 3.0 and 5.54 eV, respectively. Poly(phenylene vinylene) (PPV) based light emitting diodes using PTQx as an electron transport layer, ITO/PPV/PTQx/Al, combined low turn-on voltage (3.6 V) and high brightness ( $710 \text{ cd/m}^2$ ) with good efficiency (0.4%). The performance of PTQx as an electron transport material in electroluminescent devices was found to be far superior compared to all previously reported n-type polymers.

## Thiophene-Linked Polyphenylquinoxaline: A New Electron Transport Conjugated Polymer for Electroluminescent Devices

Yuanting Cui, Xuejun Zhang, and Samson A. Jenekhe\*  
Departments of Chemical Engineering and Chemistry  
University of Rochester, Rochester, New York 14627-0166

Electroluminescent semiconducting polymer devices are promising for display applications.<sup>1</sup> Because most current electroluminescent (EL) conjugated polymers inject and transport holes more efficiently than electrons,<sup>1,2</sup> synthesis of new and better electron transport (ET) polymers is needed to further improve device performance. n-Type conjugated polymers such as the polyquinolines,<sup>3</sup> polyquinoxalines,<sup>4</sup> polypyridine,<sup>5</sup> and polybenzobisazoles<sup>6</sup> have recently been demonstrated as ET layers in light-emitting diodes (LEDs). In this paper we report the synthesis of a new n-type, thiophene-linked, conjugated polyphenylquinoxaline (**1b**) and show that it is an excellent ET material for polymer LEDs. EL devices of the type ITO/poly(phenylene vinylene)/**1b**/Al were found to combine low turn-on voltage (3.6 V) and high brightness (710 cd/m<sup>2</sup> at 12 V) with good efficiency (0.4% photons/electron) under ambient air fabrication and operation. The preliminary results suggest that the new conjugated polyphenylquinoxaline is far superior as an electron transport material for EL devices compared to previously reported ET materials.<sup>1-6</sup>

We have previously shown that conjugated polyquinolines with diverse chain structures were good electron transport (n-type) materials whose highest occupied molecular orbital (HOMO) and lowest unoccupied molecular orbital (LUMO) levels can be significantly varied.<sup>7</sup> The increased electron deficiency of the quinoxaline ring due to an additional imine nitrogen, compared to the quinoline ring, suggested that the LUMO levels of conjugated polyquinoxalines could be lower and perhaps improve electron transport properties. The well known *p*-phenylene-linked polyphenylquinoxaline (**1a**, PPQx)<sup>8</sup> has already been reported to be an ET material for LEDs.<sup>4</sup> We synthesized and investigated the thiophene-linked derivative **1b**, poly[2,2'-

(thiophene-2,5-diyl)-6,6'-bis(3-phenylquinoxaline)] (PTQx), in order to explore the feasible HOMO/LUMO level shifts due to its acceptor-donor-acceptor structure and their consequences for polymer/polymer heterojunction LED performance.

**Monomer Synthesis.** 2,5-Bis(phenylethynyl)thiophene (**2**) was synthesized according to literature method.<sup>9</sup> Recrystallization from methanol afforded a yellow-brown product (90%), mp 84-86°C (lit. 85 °C); <sup>1</sup>H NMR (300 MHz, CDCl<sub>3</sub>, TMS)δ: 7.18 (s, 2H), 7.41 (m, 6H), 7.58 (m, 4H). 2,5-Bis(phenyloxoacetyl)thiophene (**3**): To a solution of **2** (2.84g, 10 mmol) in 50 ml dichloromethane was added 200 mg Adogen 464 (Aldrich), 80 ml water, 1.6 g NaHCO<sub>3</sub>, and 8 g KMnO<sub>4</sub>. After vigorous stirring at room temperature for 24h, TLC indicated that the reaction was complete. Sodium bisulfite (14 g) and hydrochloric acid (6 ml) were slowly added to reduce excess oxidizing agents. After rotary evaporation of CH<sub>2</sub>Cl<sub>2</sub>, filtration, and recrystallization from ethanol, yellow needle-like crystals of **3** (65%) were obtained. Mp: 94-95°C; mass spec. (EI) 348 (calc. for C<sub>20</sub>H<sub>12</sub>SO<sub>4</sub>), 348 (found); <sup>1</sup>H NMR (300 MHz, CDCl<sub>3</sub>): δ 7.56 (m, 4H), 7.70 (m, 2H), 7.83 (s, 2H), 8.10 (m, 4H); FT-IR (KBr, cm<sup>-1</sup>): 1660, 1590, 1450, 1200, 1176, 790, 683, 652.

**Oligoquinoxaline Synthesis.** 2,2'-Bis(3-phenylquinoxaline)thiophene-2,5-diyl (**4**, TQx): A solution of monomer **3** (694 mg, 2 mmol) and 1,2-phenylenediamine (216 mg, 4 mmol) in 20 ml chloroform was refluxed for 10 h. The crude product was recrystallized from ethanol to afford a yellow **4** (800mg, 85%). Mp: 312-314°C; mass spec. (EI) 492 (calc. for C<sub>32</sub>H<sub>20</sub>N<sub>4</sub>S), 492 (found); <sup>1</sup>H NMR (300 MHz, CDCl<sub>3</sub>, δ): 6.53 (s, 2H), 7.55 (m, 6H), 7.68 (m, 4H), 7.83 (m, 4H), 8.20 (m, 4H); <sup>1</sup>H NMR (300 MHz, d-nitromethane/GaCl<sub>3</sub>, δ): 7.82, 7.90, 8.42, 8.50, 8.60.

**Polymer Synthesis: PTQx (1b).** Equimolar amounts of monomer **3** (694 mg, 2mmol) and 3,3-diaminobenzidine (428mg, 2 mmol) were dissolved in 8 ml of freshly distilled m-cresol in a glass reactor fitted with a mechanical stirrer, two gas inlets, and a side arm. The reaction

mixture was stirred under argon purge at 100°C for 24 h during which progressive increase of the solution viscosity was observed. After cooling to room temperature the reaction mixture was poured into 100 ml methanol, precipitating a red polymer product which was collected by suction filtration and continuously extracted with ethanol for 24h. The product was vacuum dried at 80 °C (95% yield):  $[\eta] = 1.09 \text{ dL/g}$  in methanesulfonic acid (MSA) at 30°C;  $^1\text{H NMR}$  (300 MHz, d-nitromethane/ $\text{GaCl}_3$ ,  $\delta$ ): 7.80, 7.92, 8.65, 8.86, 9.10; FT-IR (KBr,  $\text{cm}^{-1}$ ): 3030, 1620, 1530, 1480, 1345, 1185, 1020, 800, 700, 600.

**Results.** The new tetraketone **3** was synthesized and used to prepare oligomer **4** and thiophene-linked conjugated poly(phenylquinoxaline) **1b** (scheme 1).  $^1\text{H NMR}$  spectra of the oligomer in both  $\text{CDCl}_3$  and d-nitromethane/ $\text{GaCl}_3$  and that of the polymer PTQx in the latter solvent allowed the ready assignment of the proton resonances to the polymer structure. The onset of thermal decomposition under nitrogen in thermogravimetric analysis (TGA) was 580°C. No phase transition was observed in differential scanning calorimetry (DSC) in repeated scans up to 300°C, suggesting that the glass transition of the polymer is high.<sup>4,8</sup> PTQx was completely soluble in formic acid (red), *m*-cresol (red), MSA (blue), and nitromethane/ $\text{GaCl}_3$  but it was only partially soluble in chloroform or tetrahydrofuran. A sample of PPQx (**1a**) synthesized<sup>8</sup> for comparison with PTQx had similar solubility characteristics except that it was also soluble in chloroform (yellow solution).

The intrinsic viscosity of PTQx (1.09 dL/g) was smaller than that of PPQx (1.43 dL/g) even though the thiophene-linked polymer had better film-forming properties. The reason for this difference is likely because the thiophene-linked polymer chain is more flexible compared to the 1,4-phenylene-linked PPQx. Early work on PPQx with an intrinsic viscosity of 2.62 dL/g also reported a  $\overline{M}_w$  value of 350,000.<sup>8a</sup> Thus, the measured intrinsic viscosity of the present polymers reflects moderate molecular weights.

Oligoquinoxaline **4** solutions in  $\text{CHCl}_3$  and formic acid had absorption maxima ( $\lambda_{\text{max}}$ ) of 405 nm ( $\log \varepsilon = 4.69$ ) and 448 nm ( $\log \varepsilon = 4.75$ ), respectively. The corresponding emission maxima in the same solvents were 471 and 574 nm, respectively. Surprisingly, the solution absorption and emission spectra of PTQx were only moderately red shifted from those of the oligomer. The absorption  $\lambda_{\text{max}}$  of PTQx in  $\text{CHCl}_3$  and formic acid were 414 nm ( $\log \varepsilon = 4.64$ ) and 446 nm ( $\log \varepsilon = 4.80$ ), respectively. The emission maxima of PTQx in these two solvents were 522 and 603 nm, respectively. These spectral properties of PTQx and its oligomer **4** can be understood in terms of *intramolecular charge transfer* (ICT) between the electron accepting phenylquinoxalines and electron donating thiophene moiety within the polymer repeat unit.<sup>7, 10</sup> The remarkable similarity of the absorption  $\lambda_{\text{max}}$  of oligoquinoxaline TQx and the conjugated polymer PTQx in formic acid arises from the dominant role of ICT when the quinoxaline rings are protonated and hence are stronger electron acceptor moieties.

The optical absorption and photoluminescence (PL) spectra of PTQx thin film are shown in Figure 1. The  $\pi$ - $\pi^*$  absorption maximum at 434 nm (2.86 eV) in the thin film is red shifted from that in chloroform solution (414 nm, 3.0 eV). A solid state optical band gap ( $E_g^{\text{opt}}$ ) of 2.41 eV was obtained from the optical absorption edge (Fig. 1). The solid state PL emission spectrum (430-nm excitation) shown in Figure 1 has a peak at 536 nm with a vibronic shoulder at 580 nm. The very poor fluorescence efficiency ( $<10^{-2}\%$ ) of PTQx thin film and the moderate Stokes shift (0.55 eV) suggests excimer emission<sup>11</sup> as its origin although ICT may also contribute to the rather low PL quantum yield.

Cyclic voltammetry of PTQx thin films revealed a reversible reduction and an irreversible oxidation waves. The formal potential  $E^0$  for the reduction was  $-1.60$  V (versus SCE) and the onset reduction potential was  $-1.40$  V. The oxidation had an onset potential of  $1.14$  V and a peak at  $1.38$  V. From these redox data we estimated an electrochemical band gap

( $E_g^{el} = E_{onset}^{ox} - E_{onset}^{red}$ ) of 2.54 eV, an electron affinity ( $EA = E_{onset}^{red} + 4.4$ ) of 3.0 eV and an ionization potential ( $IP = E_{onset}^{ox} + 4.4$ ) of 5.54 eV. We note that these EA and IP estimates are based on using the SCE energy level of -4.4 eV below the vacuum level<sup>7a</sup>; others<sup>4</sup> have used SCE energy levels as low as -4.8 eV which would increase the EA value of PTQx to 3.4 eV. Even the conservative EA value of 3.0 eV is still quite large, which in conjunction with the reversible reduction suggests that PTQx is a good n-type conjugated polymer with potential for application as an electron injection and transport layer in EL devices.

We fabricated polymer/polymer heterojunction LEDs of the form ITO/PPV (35nm)/PTQx (40 nm)/Al to evaluate the potential of PTQx as an electron transport material for EL devices. The poly(p-phenylene vinylene) (PPV) thin film was spin coated onto ITO coated glass from a sulfonium precursor in methanol solution followed by standard procedures (thermal conversion at 250 °C for 1.5 h).<sup>1</sup> PTQx thin film was spin coated from its formic acid solution (1 wt%) onto the PPV layer and dried at 80°C in vacuum. EL spectrum from the PPV/PTQx heterojunction device at a bias voltage of 4V is also shown in Figure 1. The EL spectrum with vibronic peaks at 532 and 568nm is identical to the PL spectrum of PPV, EL spectrum of a single-layer ITO/PPV/Al device, and other reported PPV EL spectra.<sup>1</sup>

The current-voltage and luminance-voltage characteristics of the ITO/PPV(35 nm)/PTQx (40 nm)/Al LED are shown in Figure 2. The turn-on voltage of the device is 3.6V which is much less than the 7 V observed for the single-layer ITO/PPV/Al device. The substantially lowered turn-on and drive voltages of the PPV/PTQx diode (Fig. 2) show that the new thiophene-linked conjugated poly(phenylquinoxaline) is a good electron-injecting and electron-transport material for PPV-based EL devices.<sup>1</sup> The maximum luminance of the PPV/PTQx diode is 710 cd/m<sup>2</sup>, at a current density of 400 mA/cm<sup>2</sup> and a drive voltage of 12 V, which is about 40 times as bright as the single-layer PPV diode. The corresponding maximum EL efficiency was 0.4%

photons/electron which is significantly enhanced compared to 0.01% for the single-layer PPV diode. Although comparative PPV/PPQx bilayer LEDs had a similar 3.6 V turn-on voltage, the maximum luminance achieved under similar conditions was only 80 cd/m<sup>2</sup> which means that PTQx is far superior as an electron transport material compared to existing poly(phenylquinoxalines).<sup>4, 8</sup> In fact, the present PPV/PTQx LEDs are also significantly improved compared to previously reported devices of PPV/polyphenylquinoxalines,<sup>4</sup> PPV/polypyridine,<sup>5</sup> and PPV/polyquinolines.<sup>3</sup>

Several factors may account for the observed good performance of PPV/PTQx diodes and particularly PTQx thin films as ET layers. The ready reversible electrochemical reduction of PTQx and its high electron affinity suggest efficient electron injection and transport to the PPV/PTQx interface. The HOMO/LUMO levels of PTQx (5.54/3.0 eV) relative to PPV (5.11/2.71 eV)<sup>7a</sup> ensures that there are energy barriers to electrons and holes at the interface where injection of electrons could control recombination. Absence of evidence of exciplex formation<sup>11</sup> or energy transfer at the heterojunction is also beneficial. Its high thermal stability, high intrinsic viscosity (molecular weight), and good amorphous film-forming properties are additional beneficial factors.

**Summary.** New thiophene-linked conjugated polyquinoxaline PTQx and oligoquinoxaline TQx have been synthesized and characterized. Comparison of their electronic absorption spectra revealed the dominant role of intramolecular charge transfer in their electronic structures and properties. PTQx has a reversible electrochemical reduction and high electron affinity and ionization potential which make it an attractive n-type conjugated polymer. Evaluation of PTQx as an electron transport material for PPV-based light-emitting devices showed that it was far superior to previous ET materials.

**Acknowledgment.** This work was supported by the Office of Naval Research and the National Science Foundation (CHE-9120001, CTS-9311741).




## References and Notes

- (1) For a recent review, see: Friend, R. H.; Gymer, R. W.; Holmes, A. B.; Burroughes, J. H.; Marks, R. N.; Taliani, C.; Bradley, D. D. C.; dos Santos, D. A.; Brédas, J. L.; Lögdlund, M.; Salaneck, W. R. *Nature* **1999**, *397*, 121-128.
- (2) Stenger-Smith, J. D.; Zarras, P.; Merwin, L. H.; Shaheen, S. E.; Kippelen, B.; Peyghambarian, N. *Macromolecules* **1998**, *31*, 7566.
- (3) (a) Jenekhe, S. A.; Zhang, X.; Chen, X. L.; Choong, V. E.; Gao, Y.; Hsieh, B. R. *Chem. Mater.* **1997**, *9*, 409. (b) Zhang, X.; Shetty, A. S.; Jenekhe, S. A. *Acta Polym.* **1998**, *49*, 52.
- (4) (a) Jandke, M.; Strohmriegl, P.; Berleb, S.; Werner, E.; Brütting, W. *Macromolecules* **1998**, *31*, 6434. (b) Fukuda, T.; Kanbara, T.; Yamamoto, T.; Ishikawa, K.; Takezeo, H.; Fukuda, A. *Appl. Phys. Lett.* **1996**, *68*, 2346. (c) O'Brien, D.; Weaver, M. S.; Lidzey, D. G.; Bradley, D. D. C. *Appl. Phys. Lett.* **1996**, *69*, 881.
- (5) Wang, Y. Z.; Gebler, D. D.; Fu, D. K.; Swager, T. M.; MacDiarmid, A. G.; Epstein, A. J. *Synth. Met.* **1997**, *85*, 1179.
- (6) Zhang, X.; Jenekhe, S. A. *Mater. Res. Soc. Symp. Proc.* **1998**, *488*, 539.
- (7) (a) Agrawal, A. K.; Jenekhe, S. A. *Chem. Mater.* **1996**, *8*, 579. (b) Agrawal, A. K.; Jenekhe, S. A. *Macromolecules* **1993**, *26*, 895.
- (8) (a) Hagnauer, G. L.; Mulligan, G. *Macromolecules* **1973**, *6*, 477. (b) Fang, T. *Macromolecules* **1991**, *24*, 444.
- (9) Sanechika, K.; Yamamoto, T.; Yamamoto, A. *Bull. Chem. Soc. Jpn.* **1984**, *57*, 752.
- (10) Yamamoto, T.; Zhou, Z.; Kanbara, T.; Shimura, M.; Kizu, K.; Maruyama, T.; Nakamura, Y.; Fukuda, T.; Lee, B. L.; Ooba, N.; Tomaru, S.; Kurihara, T.; Kaino, T.; Kubota, K.; Sasaki, S. *J. Am. Chem. Soc.* **1996**, *118*, 10389.
- (11) (a) Jenekhe, S. A.; Osaheni, J. A. *Science* **1994**, *265*, 765. (b) Osaheni, J. A.; Jenekhe, S. A. *Macromolecules* **1994**, *27*, 739.


### Figure Captions

**Figure 1.** Optical absorption and PL spectra of PTQx thin film and electroluminescence spectrum of an ITO/PPV (35 nm)/PTQx (40 nm)/Al LED at a bias of 4 V.

**Figure 2.** Current-voltage and luminance-voltage curves of an ITO/PPV (35 nm)/PTQx (40 nm)/Al LED. Inset shows the schematic device structure.

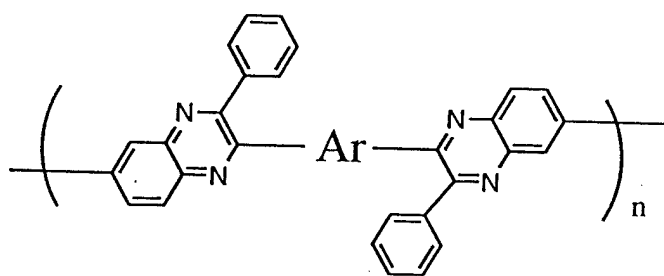

Scheme 1

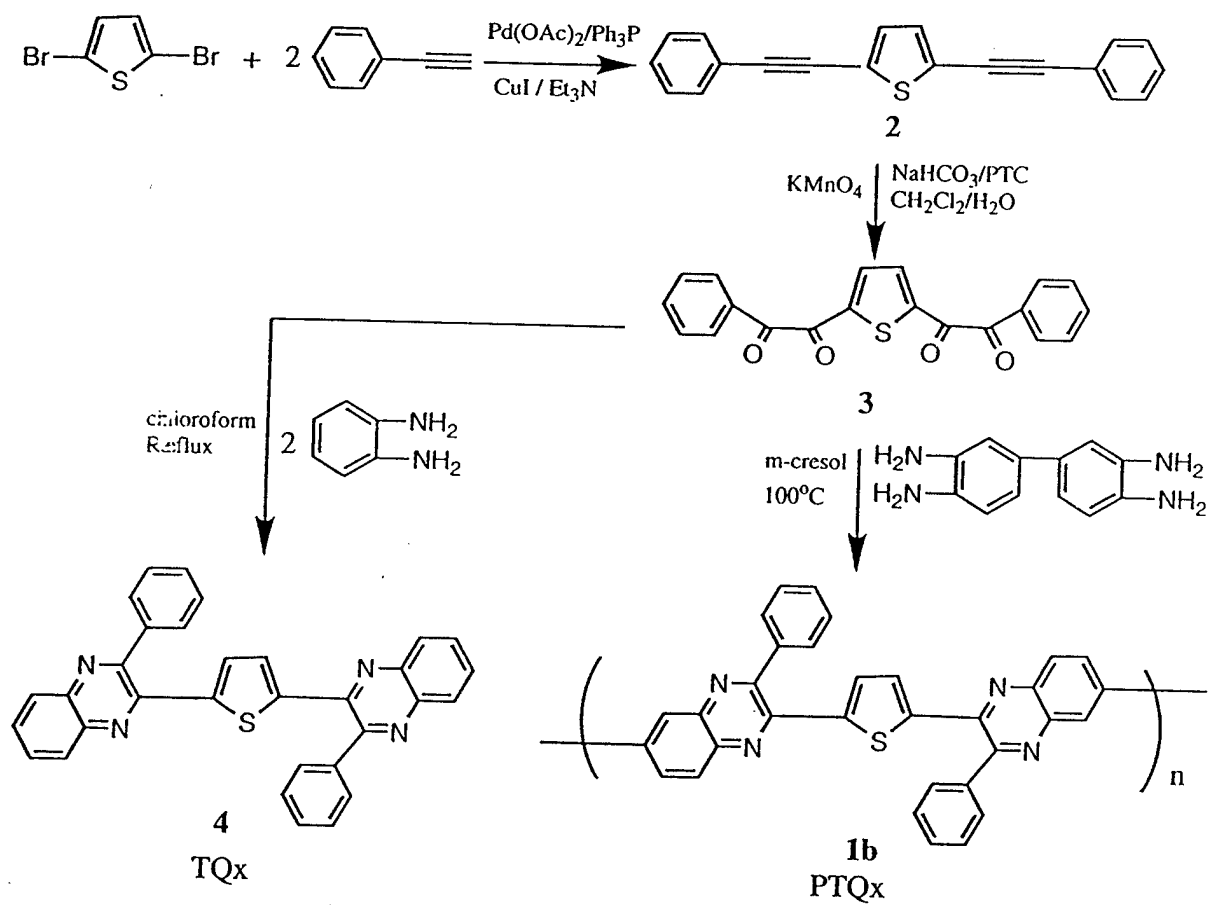


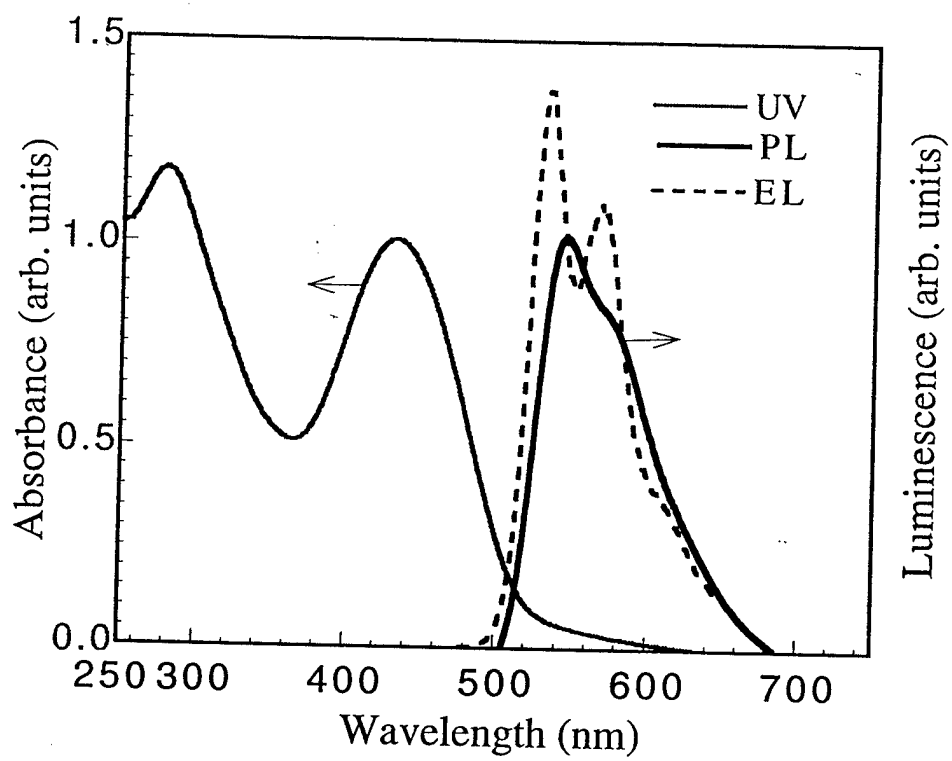


Fig.1.

Fig.2.

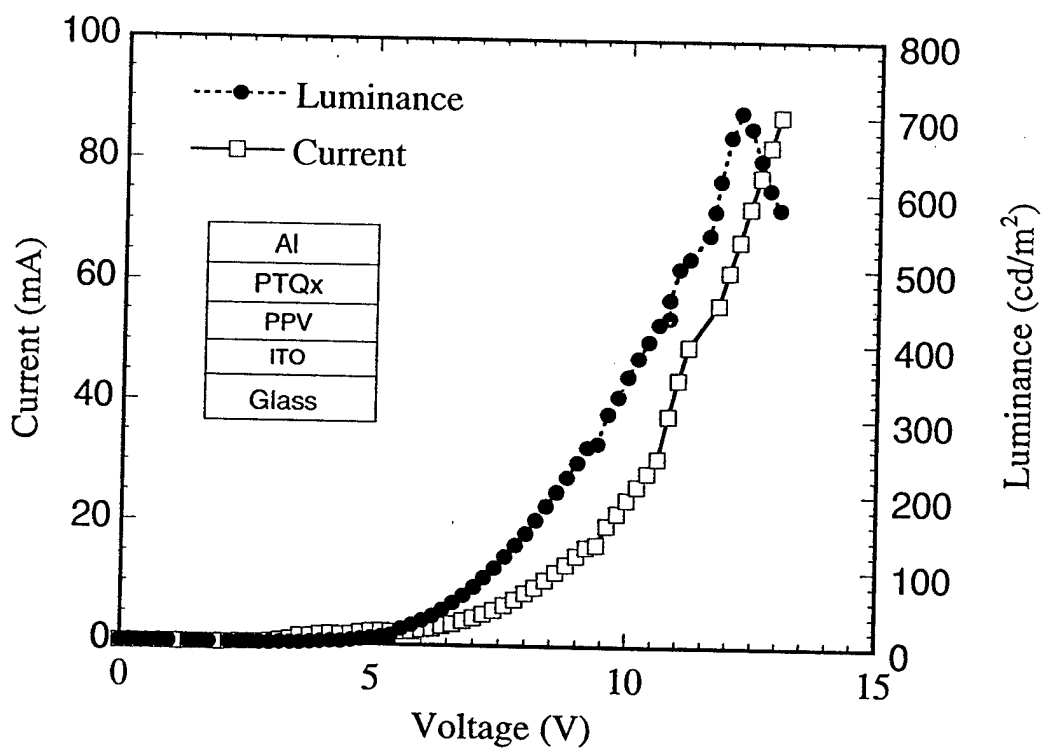

# Thiophene-Linked Polyphenylquinoxaline: A New Electron Transport Conjugated Polymer for Electroluminescent Devices

Yuanting Cui, Xuejun Zhang, and Samson A. Jenekhe\*  
Departments of Chemical Engineering and Chemistry  
University of Rochester, Rochester, New York 14627-0166

## SUPPORTING INFORMATION

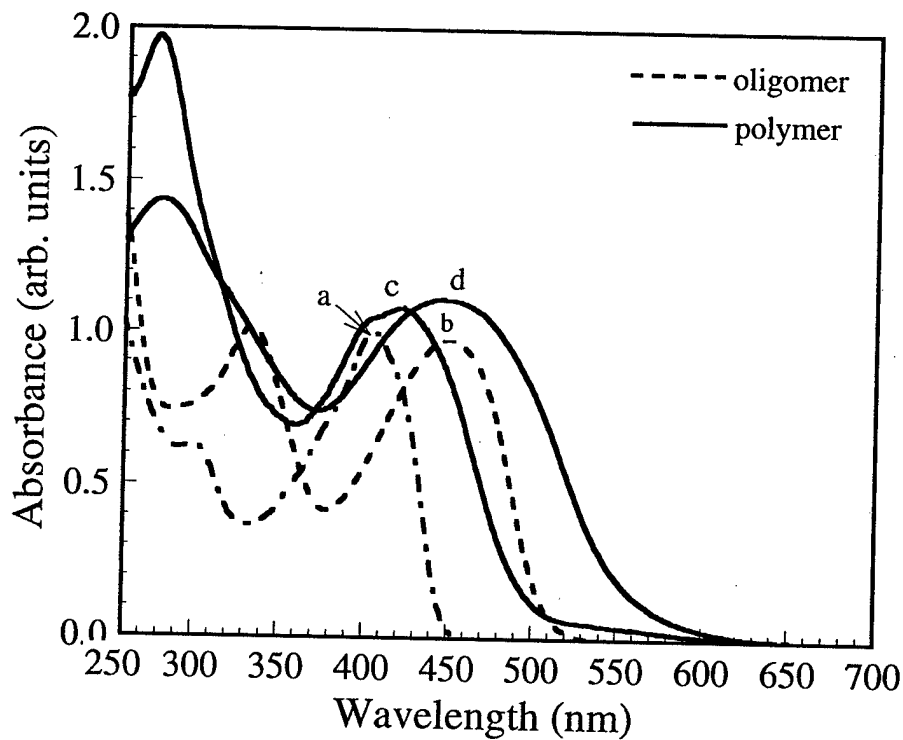


Fig. S1 UV-vis absorption spectra of TQx oligomer in chloroform (a) and formic acid (b) and PTQx polymer in chloroform (c) and formic acid (d). (All solutions are  $10^{-6}$ M)

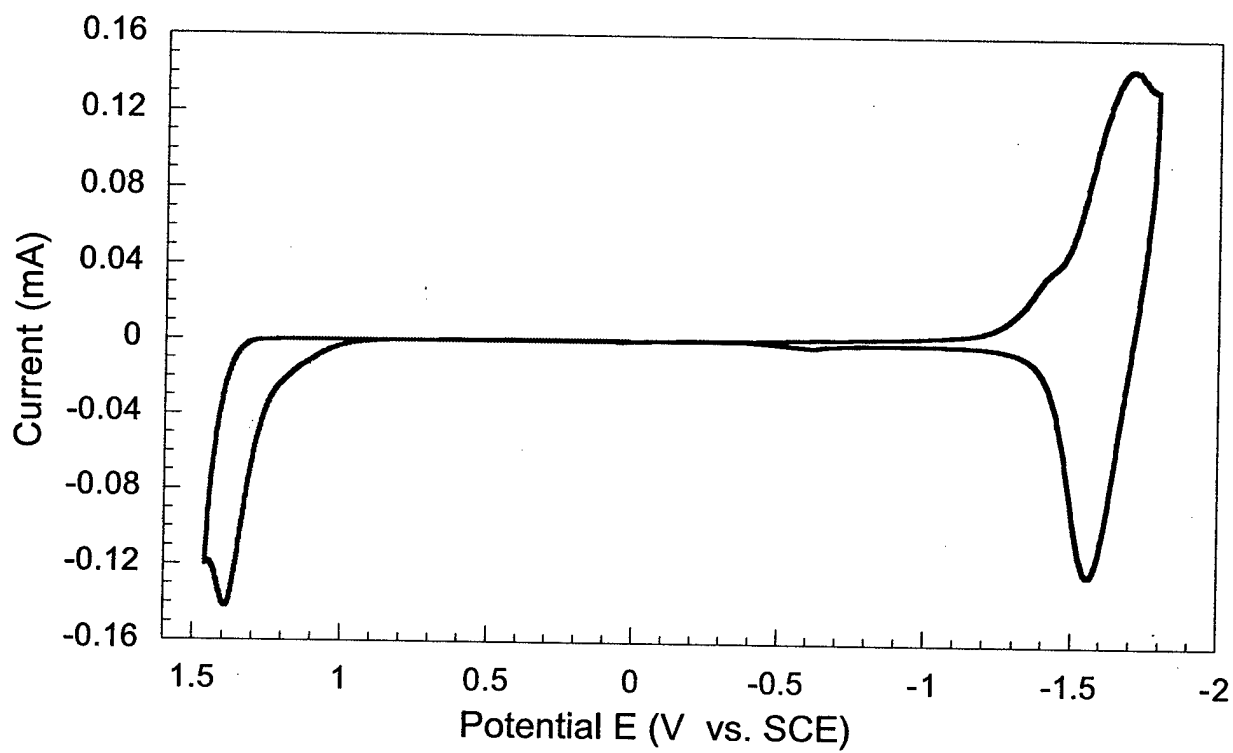


Fig S2. Cyclic voltammogram of PTQx thin film in acetonitrile with tetra-n-butylammonium tetrafluoroborate (0.1M) as the electrolyte. Scan rate: 20 mV/s.

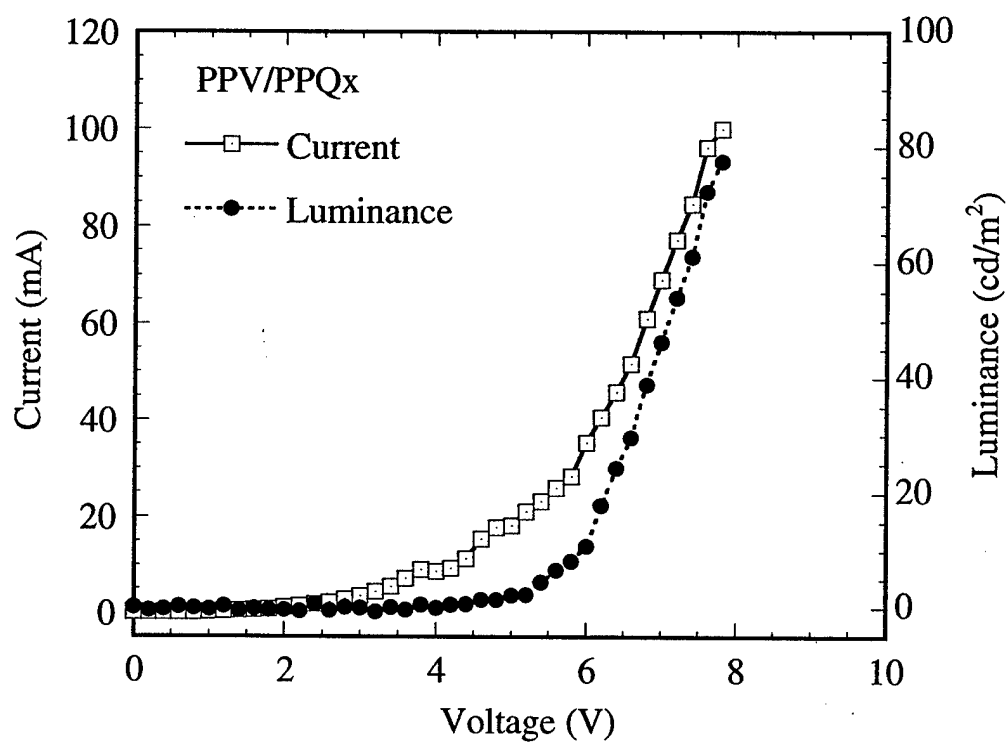


Fig. S3. The current-voltage and luminance-voltage characteristics of ITO/PPV(35nm)/PPQx(40nm)/Al device.

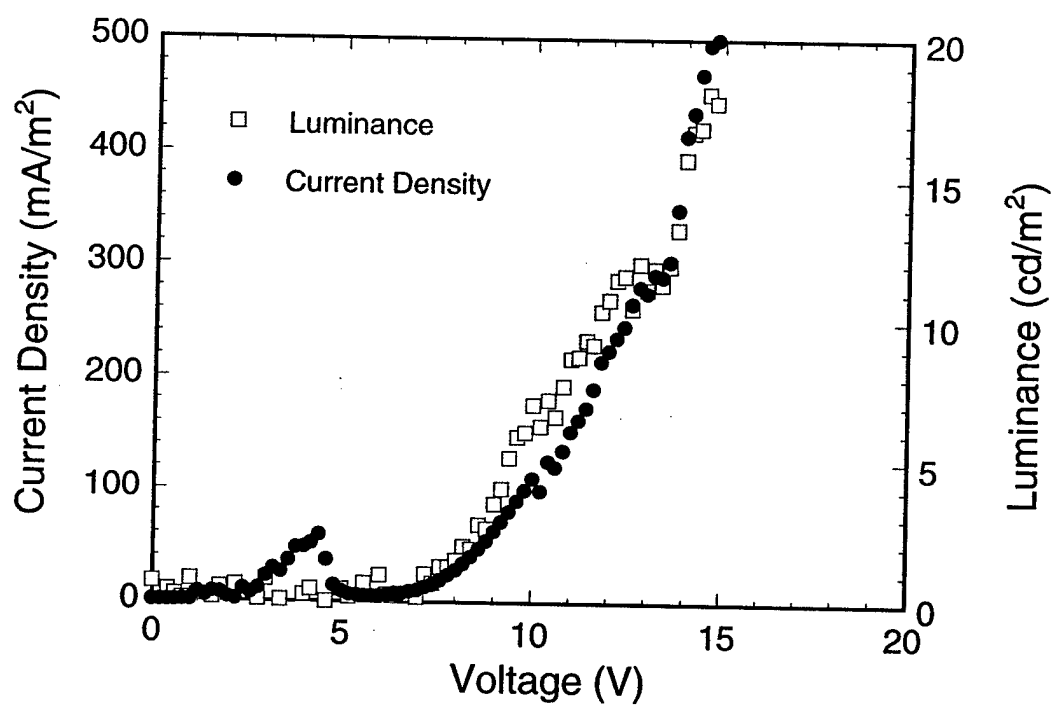


Fig. S4. The Current-voltage and luminance-voltage characteristics of ITO/ PPV (35nm) /Al device.

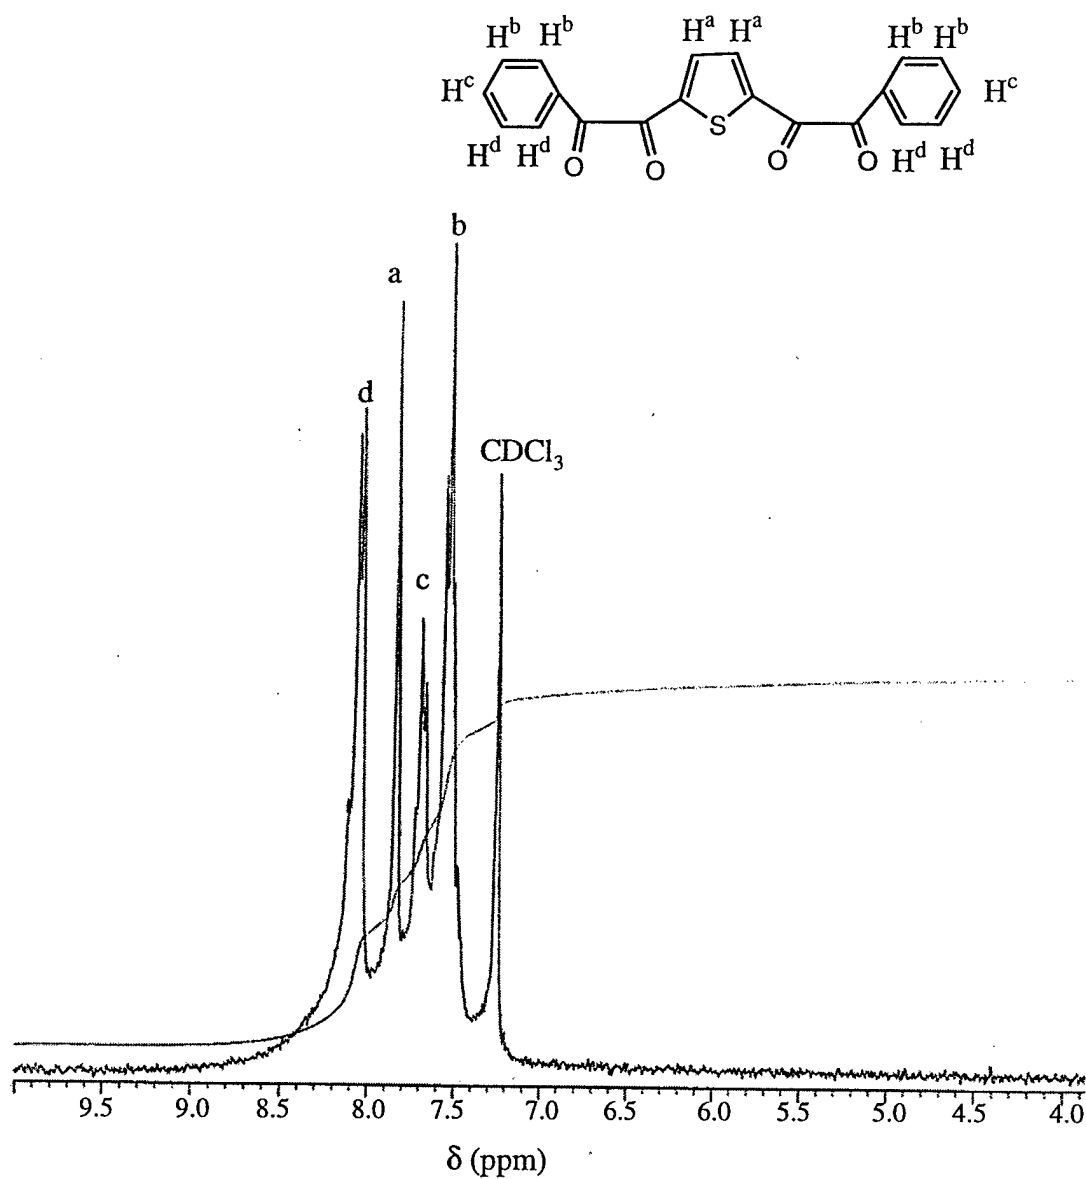


Fig. S5.  $^1\text{H}$  NMR spectrum of PTQx monomer in d-chloroform.

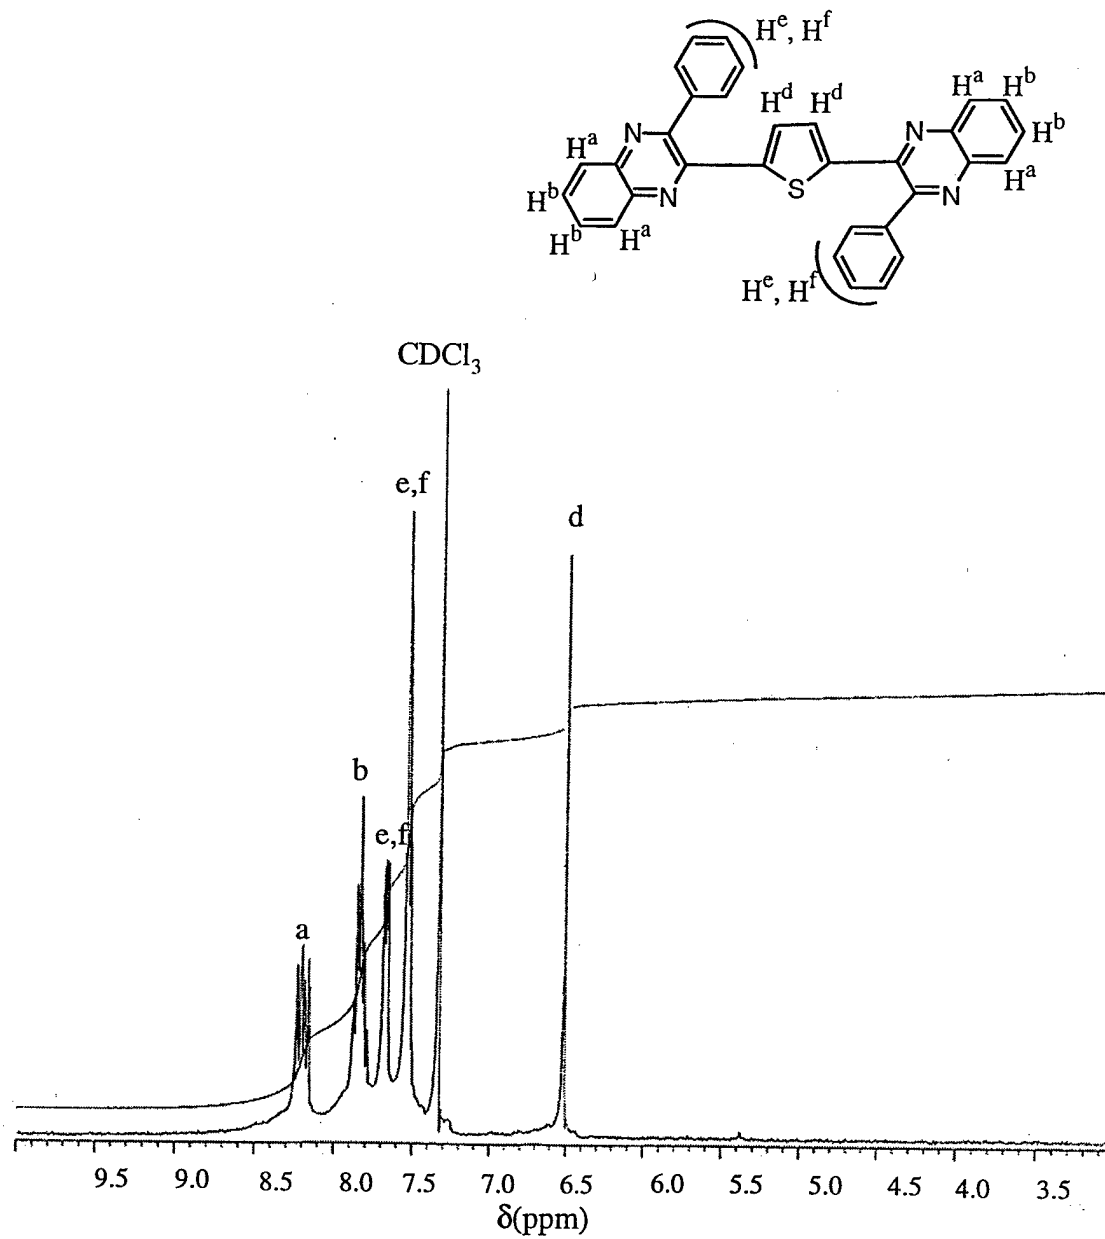


Fig. S6.  $^1\text{H}$  NMR spectrum of model compound TQx in d-chloroform.

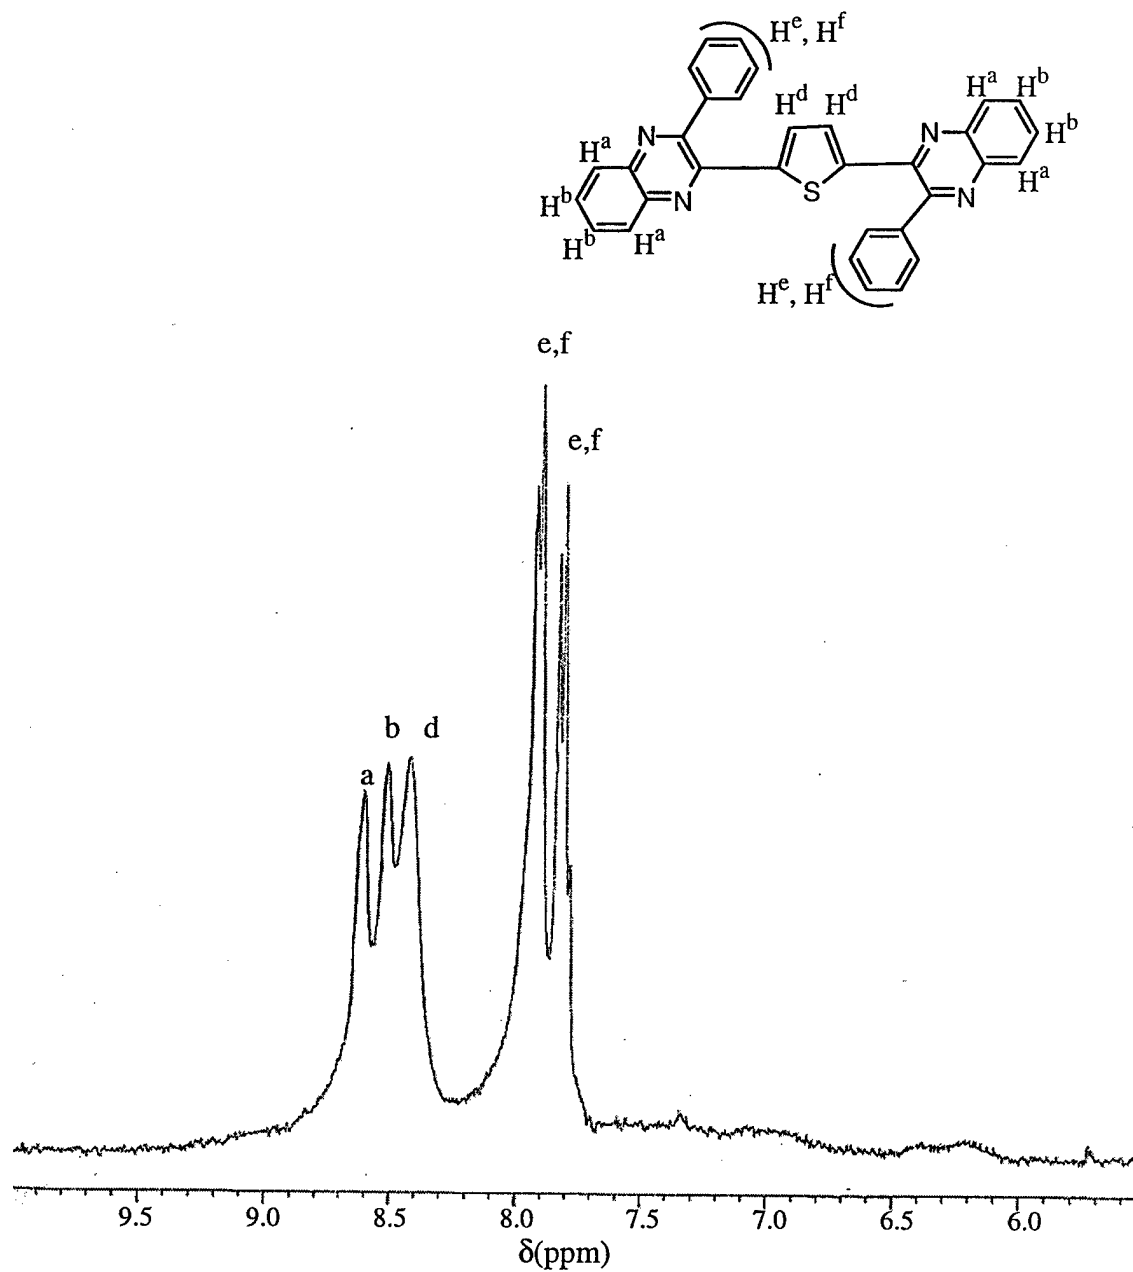


Fig. S7.  $^1\text{H}$  NMR spectrum of model compound TQx in  $\text{d-nitromethane}/\text{GaCl}_3$ .

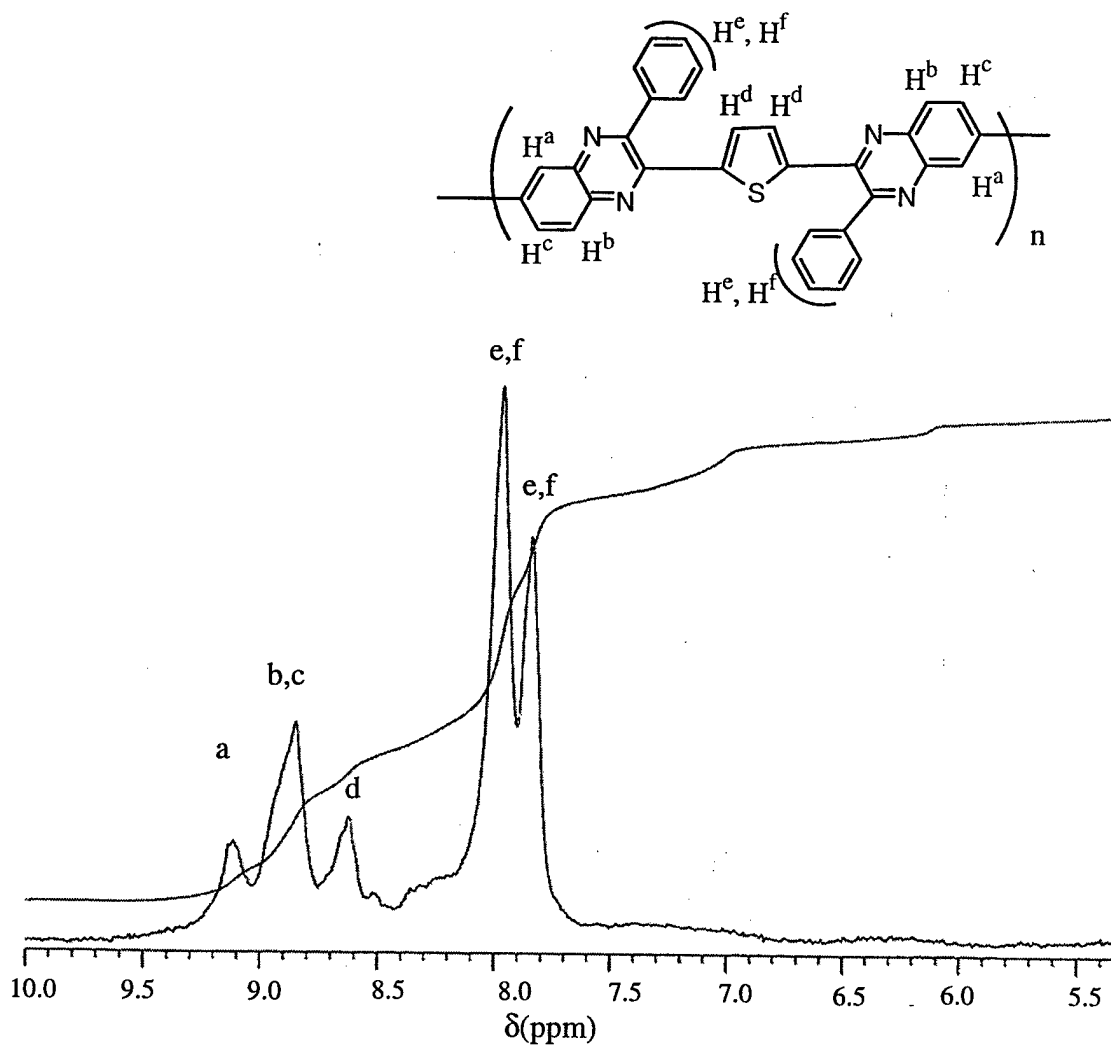


Fig. S8  $^1\text{H}$  NMR spectrum of PTQx in  $d$ -nitromethane containing  $\text{GaCl}_3$ .

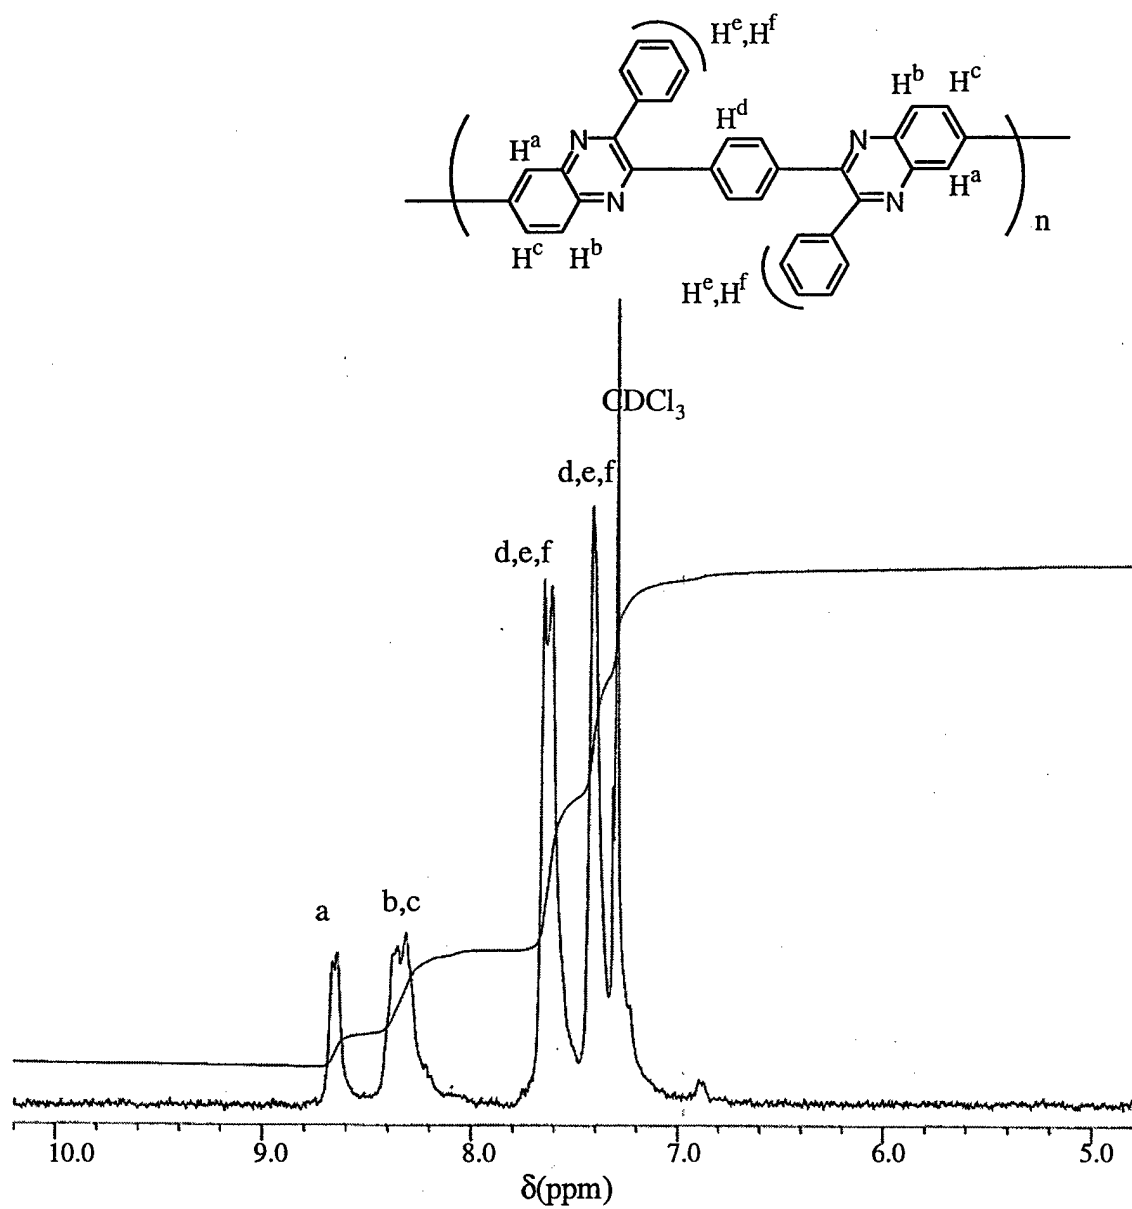


Fig. S9.  $^1\text{H}$  NMR spectrum of PPQx in d-chloroform.